

AN EXPERIMENTAL INVESTIGATION ON THE GEOENGINEERING PROPERTIES OF POND ASH-BENTONITE MIXES

Suryaleen Rout

PhD Scholar, Department of Civil Engineering, National Institute of Technology Rourkela, Rourkela – 769008, Odisha.
suryaleen1512@gmail.com

Suresh Prasad Singh

Professor, Department of Civil Engineering, National Institute of Technology Rourkela, Rourkela – 769008, Odisha.
spsingh@nitrkl.ac.in

ABSTRACT: An engineered landfill necessitates an impervious barrier to control the intrusion of groundwater into the landfill facilities and migration of leachate to the surrounding ground. The liner material should have sufficient shear strength along with highly impermeable. This paper aims at investigating certain features of a novel material that may serve as a landfill liner material as a substitute to sand-bentonite mixture. In this investigation bentonite was blended with coarse pond ash ranging from 0 to 30% by weight of the total material in 5% intervals. The compaction characteristics, strength behaviour, and permeability characteristics of these mixes are evaluated. It is observed that with bentonite content varied from 20 to 30%, the average hydraulic conductivity reduces from 3×10^{-7} to 9×10^{-9} cm^2/s for samples compacted to MDD at OMC corresponding to a compactive effort of 595 kJ/m^3 . However, when the samples are compacted with 2674 kJ/m^3 energy; the hydraulic conductivity as mentioned above is achieved at a bentonite content of 15%. With the gradual addition of bentonite the cohesion of the mixture increases whereas the angle of internal friction decreases. Hence it is concluded that sand-bentonite mixes can effectively be replaced by pond ash-bentonite mixture in the landfill liners.

KEYWORDS: *Bentonite, pond ash, land fill, permeability and strength parameters.*

INTRODUCTION

Wastes are generated more and more with increasing industrialization and population growth. Based on the safety level, these wastes can be controlled by different options such as waste reduction, separation and recycling, resources recovery through waste processing, waste transformation, and environmentally sustainable disposal on land. The most frequently used disposal option for solid waste in the landfill because of its low cost and efficiency. The core component of a waste disposal facility is its liner system. The design of liner is made so as to isolate the waste from the environment minimizing the passage of leachate into the groundwater. To ensure this the important characteristics for compacted landfill liners are selection of materials, hydraulic conductivity and strength. Usually, soil rich in clay minerals are used as compacted liner materials for their low hydraulic conductivity which is required to be less than 1.0×10^{-7} cm/s (Daniel, 1987; 1990; Benson and Trast, 1995). Instead of clay, mixture of expansive soil such as bentonite with fly ash and pond ash can be used as compacted barriers (Brian et al. 2000). The current work focus on finding an accurate mixture of pond ash and bentonite that can be used as compacted clay liner. Even though pond ash and bentonite have extremely opposite properties, when mixed together they show complimentary behavior. Pond ash is highly permeable but with the addition of bentonite the hydraulic conductivity can be reduced. Bentonite being an excellent sealant helps check the passage of leachate to the ground water (Mishra et al.; 2010). The

bulk availability of pond ash helps to reduce the cost of raw materials required for liner as well as providing their safe disposal on a large scale. A number of researcher used the pond ash and its engineering properties (Kumar et al. 1999; Arrykul et al. 2005; Subbarao et al. 2007; Ghosh et al. 2007; Ghosh et al. 2010; Bera 2010; Pradeep et al. 2013; Arvind et al. 2014). This paper investigates the geo-engineering properties of pond ash-bentonite mixes and its suitability as a land fill liner material. The non-availability of sand at all landfill sites triggers a search for an alternate material. Pond ash is an industrial waste and has the distinct advantage of a geotechnical material as it resembles the natural sand. Moreover, it has the similar mineralogical composition to conventional earth materials and needs special attention for its effective utilization rather than disposing it by consuming large land area leading to the loss of agricultural production.

MATERIALS AND METHODOLOGY

Bentonite

Bentonite is primarily composed of the montmorillonite group of minerals. Commercial sodium based bentonite procured from local market is used in this experimental investigation.

Pond ash

Pond ash used in the present investigation was collected from ash pond of National Thermal Power Plant (NTPC) Talcher, Odisha. The samples were mixed thoroughly to bring homogeneity and dried at an oven temperature of 105-110°C. These were stored in

airtight containers for subsequent use. The physical properties of the bentonite and pond ash are presented Table 1.

Methodology

In this present study, synthetic mixes are prepared by adding bentonite of 5 to 30% by weight at 5% intervals with the pond ash. In this manner, six different mixes were synthesized. The OMC and MDD of these mixes corresponding to both standard and modified proctor energy are determined as per IS: 2720 (Part 7) 1980 and IS: 2720 (Part 8) 1983 respectively. Prior to the compaction tests, these synthetic materials were mixed with initial water and were kept in an airtight container for 48 hours for proper distribution of water in the mix. To find out the shear strength parameters synthetic mixes were compacted in standard Proctor mold to their respective MDD at OMC using both the standard and modified proctor energy. Undisturbed specimens of size 60mm×60mm×25mm were recovered from the mold and were sheared at a rate of 0.2 mm/min. The shear parameters (i.e. c and Φ values) were found out from the plots between normal stress and shear stress. These tests were performed as per IS: 2720 (Part 13) 1986. Unconfined compressive strength tests on specimens compacted to their corresponding MDD at OMC was performed according to IS: 2720 (Part 10) 1991. The cylindrical test specimens were of size 50mm in diameter and 100mm in height, and these were sheared at an axial strain rate of 1.25 mm/min. Hydraulic conductivity of different pond ash-bentonite mixes, compacted to their respective MDD at OMC are evaluated as per IS: 2720(Part 17) 1987.

Table 1 Physical property of pond ash and bentonite

Physical Parameters	Pond ash	Bentonite
Fines content, <75µm (%)	1.99	96.93
Fine sand (%)	64.28	3.07
Medium sand (%)	33.73	0
Uniformity coefficient, C _u	1.15	-
Coefficient of curvature, C _c	2.91	-
Specific gravity	2.23	2.7
Liquid limit	-	301
Plastic limit	-	65
Plasticity index	NP	236
Soil type	SP	CH

RESULT AND DISCUSSION

Compaction characteristics

Figure 1 shows that with the addition of bentonite, the OMC value decreases up to an optimum bentonite content after that it remains almost unchanged. Figure 2 shows the variation of maximum dry unit weight with bentonite content. It is found that with the addition of bentonite to pond ash, maximum dry unit weight value increases up to an optimum bentonite content after that

it remains almost constant. This trend is observed for samples compacted either with standard or modified proctor energy. The optimum content of bentonite for both the cases is found to be 20%. This may be due to the fact that when bentonite percentage is small, the finer particles of bentonite mostly go into the intra-void spaces present in the conglomerated ash particles. As the percentage of bentonite is further increased, these particles filled-up the inter-particle void spaces available in the pond ash sample. This increases the maximum dry unit weight value. Further increase of bentonite creates a space for itself forcing the ash particles to move apart, thus stabilizing the maximum dry unit weight value.

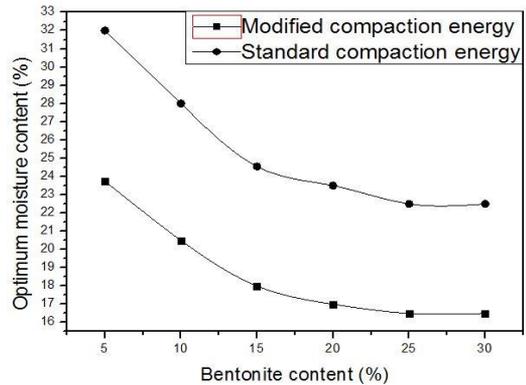


Fig. 1 Variations of optimum moisture content with bentonite content

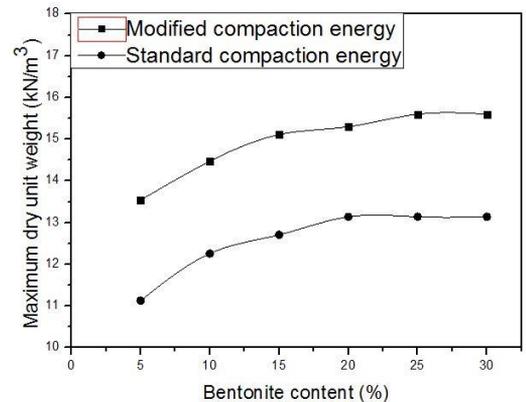


Fig. 2 Variations of maximum dry unit weight with bentonite content

Hydraulic conductivity

The variation of hydraulic conductivity with bentonite content is shown in Figure 3. It is obvious that an increase of bentonite content in the compacted mixtures lowers the hydraulic conductivity values. This has been verified by many studies. Since bentonite alone has characteristics of impervious material and has extremely low hydraulic conductivity values in the order of 10⁻¹⁰ to 10⁻¹² cm/s, it is expected to have lower hydraulic conductivities as its percentage in the mixture increases. The experimental data shows that

the reduction in hydraulic conductivity with bentonite content is not linear. Initially, the rate of reduction is mild followed by a sharp decrease in the hydraulic conductivity value. At low bentonite content, the finer bentonite particles get adjusted in the intra-particle void space of pond ash thus there is an appreciable reduction in capillary void space. However, as its content increases it reduces the capillary void thus a sharp reduction in the hydraulic conductivity value.

Unconfined compressive strength

Unconfined compressive strength test was performed for sample prepared with both standard and modified compaction energy. Compressive strength of pond ash-bentonite mixture compacted for both the energy were found to be in the range of 52 to 197 kPa and 99 to 691 kPa respectively as shown in Figure 4. As per the general requirement of isolation material such as liner, the compressive strength should have a value more than 200 kPa. The above strength is accomplished for the samples containing 15% or above bentonite and prepared with modified compaction energy.

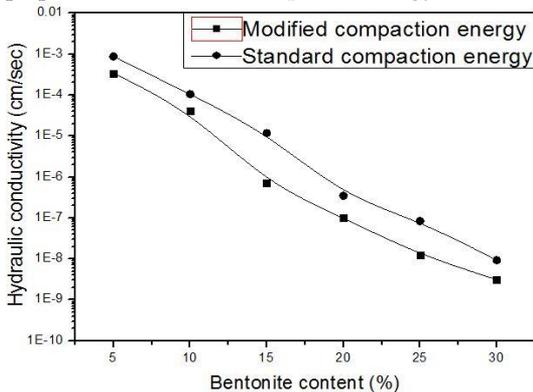


Fig. 3 Variations of Hydraulic conductivity with bentonite content

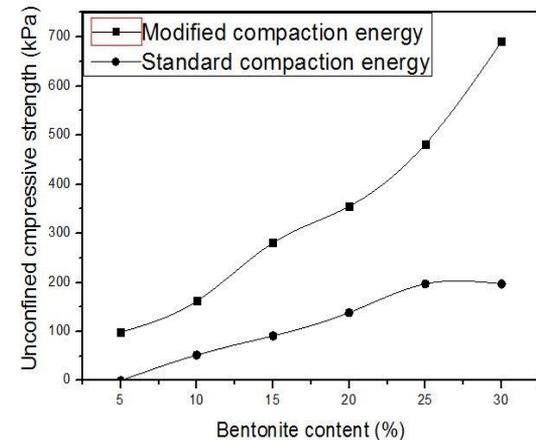


Fig. 4 Variations of unconfined compressive strength with bentonite content

Shear strength parameters

Shear strength parameters such as unit cohesion (c) and internal angle of friction (ϕ) were found to be in the range of 16.27 to 63.81 kPa and 42.5° to 28.4° for mixtures prepared with standard compaction energy, 12.67 to 89.59 kPa and 44.6° to 30.9° for the mixtures prepared with modified compaction energy when the bentonite content of the mixture is changed from 5 to 30%. Figure 5 and 6 presents the variation of unit cohesion and angle of internal friction with bentonite content. It is seen that as the bentonite content increases, the cohesion increases and internal friction angle decreases. This may be due to the fact that as pond ash particles are irregular in shape, there exist a good interlocking between the particles hence the angle of internal friction is high. When a smaller amount of bentonite is added to the mixture, the finer particle of bentonite tries to fill the intra-void spaces present in the conglomerated ash particles. But as the bentonite content increases, the excess bentonite coats the surfaces of the ash particle. As bentonite particles are lubricative in nature, the bentonite coated pond ash particles loses their contact and slips over each other and hence frictional angle decreases. However, due to the presence of strong inter-particle attractive forces between the bentonite particles the mixture gradually develops cohesion with an increase in bentonite content.

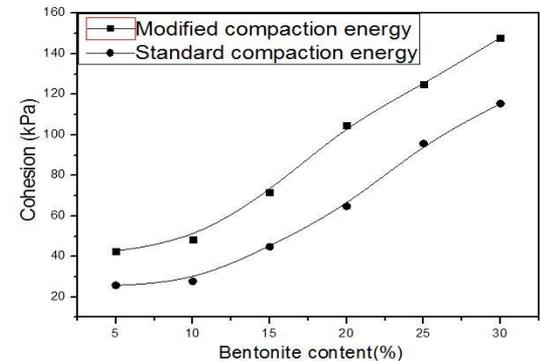


Fig. 5 Variations of cohesion with bentonite content

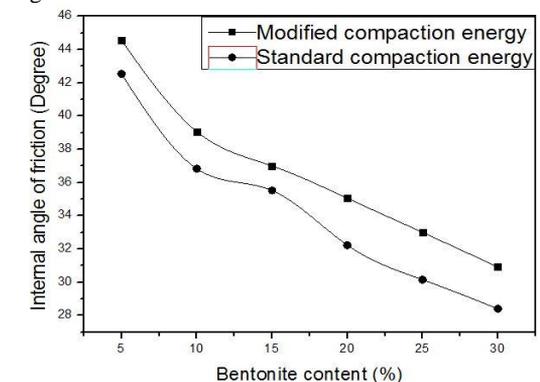


Fig. 6 Variations of internal angle of friction with bentonite content

CONCLUSION

The suitability of pond ash-bentonite mixes as landfill liner material was investigated in this work. Based on the experimental investigation, the following conclusions are drawn:

- Samples compacted with standard compaction energy the maximum dry unit weight increases from 11.13 to 13.14 kN/m³ and the corresponding OMC of the mixtures decreases from 32 to 22.5% as the bentonite content varies from 5 to 30%. However, with modified compaction energy, the maximum dry unit weight increases from 13.54 to 15.6 kN/m³ and the corresponding OMC decreases from 23.75 to 16.5%
- Hydraulic conductivity values of bentonite-pond ash mixes compacted with both standard and modified compaction energy were found to be in the range of 8.83×10^{-4} to 9.23×10^{-9} cm/s and 3.42×10^{-4} to 5.15×10^{-9} cm/sec with a change in bentonite content from 5 to 30% respectively.
- Compressive strength of pond ash-bentonite mixture compacted for both the energy were found vary from 52 to 197 kPa and 99 to 691 kPa respectively.
- Shear strength parameters such as cohesion (c) and internal friction angle (ϕ) were found to be in the range of 16.27 to 63.81 kPa and 42.54° to 28.4° for mixtures prepared with standard compaction energy. These values are 12.672 to 89.59 kPa and 44.55° to 30.90° for the mixtures prepared with modified proctor energy.

From this study, it can be concluded that sand bentonite mixture can effectively be replaced by pond ash bentonite mixture when sand is not easily available and wastes are to be utilized.

References

- Akcanca, F., & Aytakin, M. (2012) 'Effect of wetting–drying cycles on swelling behavior of lime stabilized sand–bentonite mixtures.' *Environmental Earth Sciences*, 66(1), pp67-74.
- Alam, J., Khan, M. A., Alam, M. M., and Ahmad, A. (2012) 'Seepage characteristics and geotechnical properties of flyash mixed with bentonite.' *International Journal of Scientific Engineering Research*, 3(8), pp1-11.
- Auvray, R., Rosin-Paumier, S., Abdallah, A., and Masrouri, F. (2014) 'Quantification of soft soil cracking during suction cycles by image processing.' *European Journal of Environmental and Civil Engineering*, 18(1), pp11-32.
- Bose, B. (2012) 'Geoen지니어ing properties of expansive soil stabilized with flyash.' *Electronic Journal of Geotechnical Engg.*, 17, pp1339-1353.
- Chalermyanont, T. and Arrykul, S. (2005) 'Compacted sand-bentonite mixtures for hydraulic containment liners.' *Songklanakarın Journal of Science and Technology*, 27(2), pp313-323.
- Cho, W. J., Lee, J. O., & Kang, C. H. (2002) 'Hydraulic conductivity of compacted soil-bentonite mixture for a liner material in landfill facilities.' *Environmental engineering research-Seoul-*, 7(3), pp121-128.
- Kaya, A. and Durukan, S. (2004) 'Utilization of bentonite-embedded zeolite as clay liner.' *Applied Clay Science*, 25(1), pp83-91.
- Kayabali, K. (1997) 'Engineering aspects of a novel landfill liner material: bentonite-amended natural zeolite.' *Engineering Geology*, 46(2), pp105-114.
- Laskar, A. and Pal, S. K. (2013) 'Effects of waste plastic fibres on compaction and consolidation behavior of reinforced soil.' *Electronics Journal of Geotechnical Engineering*, 18, pp1547-1558.
- Mir, B. A. (2013) 'Effect of fly ash on swelling potential of BC soil.' *In Proceedings of Indian Geotechnical Conference on Geotechnical Advances and Noval Geomechanical Applications, December, Roorkee*, pp1-9.
- Mishra, A. K., Ohtsubo, M., Li, L. Y. and Higashi, T. (2010) 'Influence of the bentonite on the consolidation behaviour of soil–bentonite mixtures.' *Carbonates and evaporites*, 25(1), pp43-49.
- Mollamahmutođlu, M., and Yilmaz, Y. (2001) 'Potential use of fly ash and bentonite mixture as liner or cover at waste disposal areas.' *Environmental Geology*, 40(11-12), pp1316-1324.
- Satyanarayana, P. V. V. (2013) 'Utilization of red soil bentonite mixes as clay liner materials.' *International Journal of Scientific & Engineering Research*, Volume 4, Issue 5, pp876-882.